

Study of Pre-Mix and Post-Mix Techniques for Effective Incorporation of Nano Silica in Concrete

Haard Shukla¹, Harshit Dubey², Devindar Singh³, Abhiraj Jadeja⁴, Naimish Bhatt^{5*}

¹Pandit Deendayal Energy University

Knowledge Corridor, Raisan, Gandhinagar, Gujarat, India

Haard.scv20@sot.pdpu.ac.in ; Harshit.dcv20@sot.pdpu.ac.in

²Pandit Deendayal Energy University

Knowledge Corridor, Raisan, Gandhinagar, Gujarat, India

Abstract - In the paper, the integration of nanoparticles, particularly nano-silica, has emerged as a transformative force in enhancing material properties. This paper presents a detailed investigation that scrutinizes the impact of nano-silica on cement paste when introduced before or after the mixing process. By taking advantage of the filler effect of nano-sized particles, nano-silica has shown remarkable potential in increasing the compressive strength of cement paste, mortar, and concrete, leading to the development of denser and more resilient products. The results obtained from both pre-mix and post-mix samples reveal a trend of increasing strength up to a certain percentage of nano-silica incorporation, beyond which a slight decrease is observed. The study demonstrates that a nano-silica percentage of 3.5% yields optimal strength, with a subsequent decline in strength at higher incorporation levels. Moreover, the investigation highlights the superiority of post-mix samples in terms of strength gain, with notable improvements observed at 7, 14, and 28 days. The findings underscore the critical importance of the incorporation technique employed, with post-mix techniques showing enhanced strength gains compared to pre-mix methods. By studying the relationship between tiny particles of silica (called nano-silica) and materials used in cement production (called cementitious matrices), research aim to better understand how these materials interact and how they can be used to make stronger and more durable concrete structures, this study paves the way for innovative advancements in construction materials. It offers a compelling case for the strategic utilization of nano-silica to elevate the quality and durability of infrastructure projects.

Keywords: Nano-silica, Cement paste, Compressive strength, Pre-mix technique, post-mix technique, Concrete properties, Nanoparticles, Material composition Construction industry Infrastructure durability

1. Introduction

Over the recent years, the utilization of nanoparticles has significantly contributed to the improvement of cement and concrete properties. Among the nanoparticles that have been implemented in cement research, nano-silica stands out as the most widely used, building upon the successful application of silica fume in cement products. The introduction of nano-silica has shown remarkable potential in enhancing the compressive strength of cement paste, mortar, and concrete by using the filler effect of nano-size particles, resulting in denser products. Various research scholars have conducted extensive studies on the complex challenges associated with nano-silica. However, there are only a few reports on the mixing of cement-based materials with nano-silica, making it crucial to examine the effect of adding nano-silica either before or after mixing cement paste. In this paper, we present the results of a comprehensive study that investigates the effect of nano-silica on cement paste when added before or after mixing.

Literature Review

[1] explored using nano-waste ceramic (NWC) and nano silica (NS) to enhance Portland cement concrete performance. The study evaluated NS and NWC replacement levels, including a hybrid mix of both, which could revolutionize the construction industry. The results showed that pre-soaking recycled coarse aggregates in NS solution improved the recycled aggregate concrete's compressive strength by 5% compared to direct NS mixing. The volume of large capillary pores in the matrix adjacent to RCA is increased when NS is directly mixed but reduced when RCA is pre-soaked in NS solution. The

microstructure of the matrix adjacent to pre-soaked RCA is more compact than that of the direct mixing method. The findings of this study provide valuable insights into the use of demolition waste to create sustainable building materials. Using NS and NWC in concrete has the potential to significantly reduce the environmental impact of the construction industry. [2] explores the use of demolition waste to create sustainable building materials, focusing on enhancing concrete production using nano-waste ceramic (NWC) and nano silica (NS). The research shows that adding up to 6% NWC content in concrete improves its strength and outperforms traditional methods. The study also found that even when using up to 10% NWC content, the strength of the concrete is still impressive. The utilization of NS and NWC in concrete improves its internal structure, decreases porosity, and enhances the density of the cement matrix. The study highlights the potential of substituting cement with NS and NWC, demonstrating their positive impact on the mechanical properties of the concrete. [3] (nS) can enhance ultra-high-performance concrete (UHPC) by improving its strength, flowability, and transport properties. It can also reduce capillary pores, resulting in a finer pore structure, and improve interfacial transition zone, leading to increased durability. Replacing 3 wt.% of cement with nS can improve concrete durability, and it can resist chloride penetration and water permeability. The transport properties of concrete are influenced by its pore structure, including total porosity, pore size, pore connectivity, and pore saturation. Adding nS to UHPC has a significant impact on its overall performance. [4] Investigated the correlation between the fractal dimension of concrete and its pore structure, strength, and permeability when incorporating silica fume. Various tests were conducted to evaluate the mechanical properties and microstructure, and the results showed that silica fume improves the homogenization and refinement of the pore structure, while meso and coarse porosities have opposing effects on strength. [6] Investigated the effects of various nanoparticles on high-performance concrete (HPC). The study found that the optimal improvement in HPC could be achieved by replacing 4% of cementitious materials with nano fly ash and nano silica fume. These nanoparticles demonstrated a significant enhancement in the mechanical properties of HPC. Moreover, the study discovered that nano clay and TiO₂ nanoparticles had an impact on the mechanical properties and microstructure of cement mortars. Finally, the study identified superplasticizer as a useful component in producing high-quality concrete mix with high strength.

2. Materials and Method

Effective selection of materials along with proper mixing and incorporation of nano materials helps in attaining the desired results. Moreover, the obtained result is widely varied based on the incorporation technique employed. Different materials were used in the current study to evaluate the effect of pre mixing and post mixing of nano silica in concrete mix. In the present study the Ordinary Portland cement (OPC 53) produced by Ultratech Pvt. Ltd. conforming to international quality standards ISO 9001 was used. Graded fine (sieve no. 4 = 4.75 mm) and coarse aggregate were purchased from Sand Sure Enterprise, Gandhinagar, India. The silicon dioxide nano material (SiO₂) was supplied by Fibrezone India. Different methods of incorporation of nano silica involved:

2.1 Method of Incorporation

Pre mixing

The pre-mixing or dry mixing method is a widely-used technique in the construction industry for preparing concrete. This method involves mixing the materials in a dry state before adding water and superplasticizers. The dry mixing process allows for better control over the mixing process and helps achieve a consistent mix. Additionally, it reduces the amount of water required to make the concrete, leading to a stronger and more durable final product. The use of superplasticizers further enhances the workability of the concrete. The figure provided below illustrates the dry mixing process employed in the present study, providing a visual representation of the various stages involved.

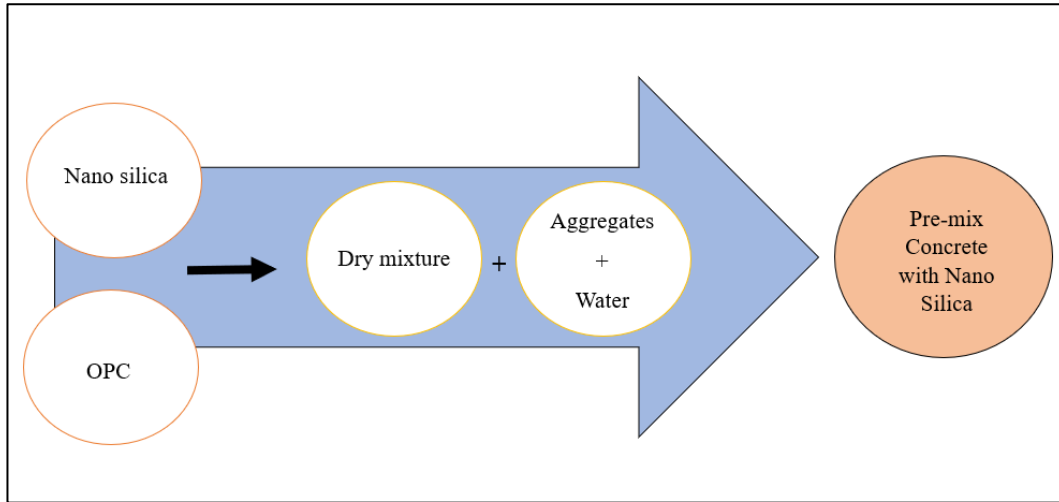


Figure 1: Pre-mix technique

[4] had employed the premixing technique for incorporation of supplementary material to cement. This method involves firstly mixing the required amount of nano silica with weighed cement in a dry state. Next this dry mixture is poured in mixer with aggregates in dry states and is mixed for 4-5 minutes, after that a required amount of water is added to obtain the concrete mix. The sample prepared are depicted in the table below.

Table 1: Pre mix specimens

Sample no.	Symbol	Nano-silica (%) by wt.
1	CDS1	0 %
2	CDS2	1%
3	CDS3	2%
4	CDS4	2.5%
5	CDS5	3%
6	CDS6	3.5%
7	CDS7	4%

The prepared mixture of concrete was the poured in the molds. However, to ease the comparison of the samples similar number of cubes of size 15 x 15 x 15 cm were prepared.

Post mixing

Post mixing or the wet mixing method is a technique used widely by for material incorporations. In this methos the nano material is not directly used, rather it is initially mixed with a liquid (water or superplasticizer) to prepare a paste. This prepared paste is then used in concrete sample for incorporation of nano materials. The post mixing method employed is depicted in below figure.

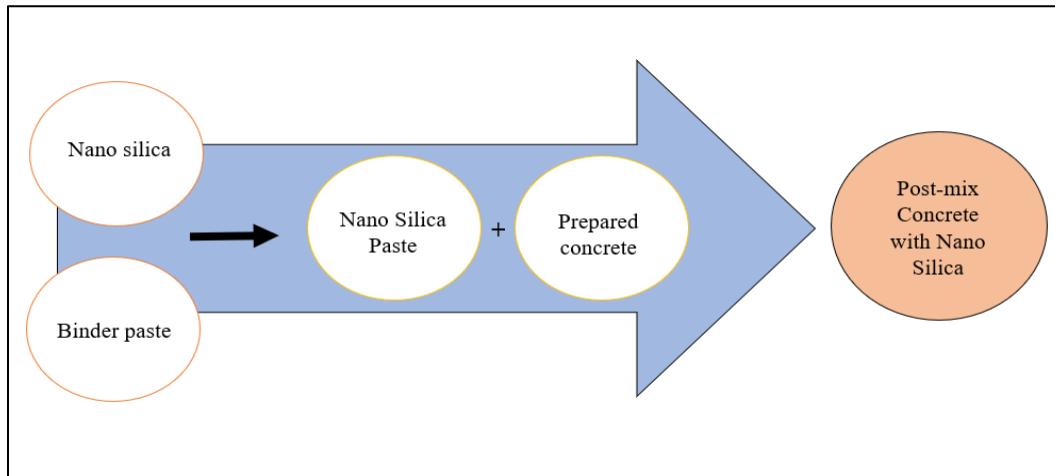


Figure 2: Post-mix technique

Different researchers have used the post mixing technique to incorporate nano materials in concrete. [2], [3]. This method follows a certain step including firstly making a paste of nano material with water, the adding this prepared paste into the concrete mix. Thus, resulting in concrete with incorporated nano materials. The samples prepared in post mix technique is tabulated below.

Table 2: Post mix specimens

Sample no.	Symbol	Nano-silica (%) by wt.
1	CWS1	0 %
2	CWS2	1%
3	CWS3	2%
4	CWS4	2.5%
5	CWS5	3%
6	CWS6	3.5%
7	CWS7	4%

Prepared concrete from the pre and post mix method with different nano silica percentage of 0%, 1%, 2%, 2.5%, 3%, 3.5%, 4% is poured in mold of size 15 x 15 x 15 cm and was cured using conventional methos. The material composition of the concrete mix show in the table below.

Table 3: Material composition in concrete mix

MATERIALS	OPC	Fine aggregate	Coarse aggregate	Water
WEIGHT (g)	17045	32000	63500	7500

The prepared cubes were tested for 7days, 14 days and 28 days under the compression testing machine. The average reading of three cubes for one sample were noted as mean compressive strength of the cube. The characteristic compressive strength was attained subtracting the standard deviation from the mean value.

3. Result and Discussion

The results obtained in both pre-mix and post-mix samples shown the trend of increasing strength to a fixed percentage of nano silica. After a certain percentage the strength shown a little increase and then started to decrease. The The obtained result shows the increase in strength to a percentage of 3.5% of nano silica incorporated in concrete, the 4% 4% incorporation showed a trend of a minute decrease in both techniques. The individual result obtained is presented below.

3.1 Pre-Mix Method

The figure 3 presents the compressive strength results for the pre-mix samples for the period of 7, 14 and 28 days. The sample CDS6 shown the maximum strength having the nano silica percentage of 3.5%. further the sample CDS7 with 4% nano silica replace with mass of concrete shown a minute decrease strength. The sample also have decrease strength when compared to the post mix samples.

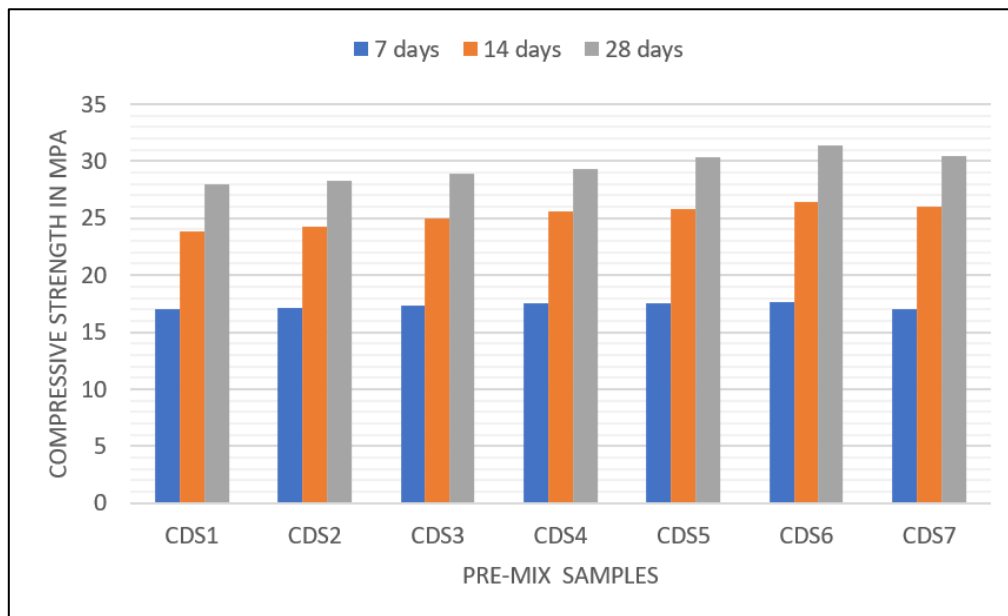


Figure 3: Pre mix samples compressive strength for 7, 14, 28 days

3.2 3.2 Post-Mix Method

The figure 4 represent the compressive strength results for the post-mix samples for the period of 7, 14 and 28 days. The sample CWS6 shown the maximum strength having the nano silica percentage of 3.5%. further the sample CWS7 with 4% nano silica replace with mass of concrete shown a minute decrease strength. Post mix samples depicted a better strength relatively to pre-mix samples. The post-mix samples shown the increase in the strength gain as present 12.85 ,13.83 and 16.02 for 7 ,14 and 28 days respectively which is in proximity with result obtained by studies [6].

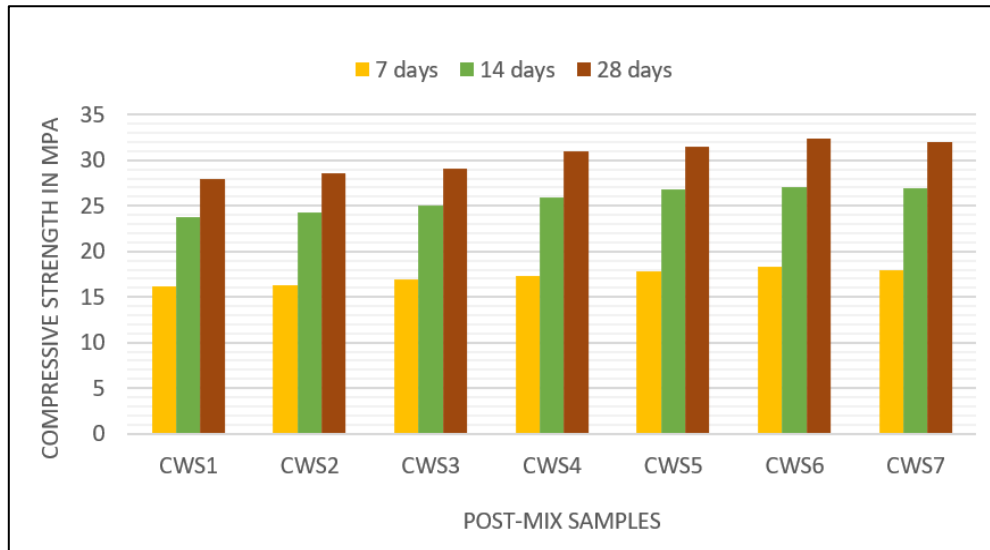


Figure 4: Post mix samples compressive strength for 7, 14, 28 days

The figure 5 present the individual comparison of post and pre-mix samples strength for 7 days, 14 days and 28 days. The pre-mix sample depicted decreased strength in all three-test period which can be due to certain reasons. These reasons include generation of deficiency which leads to creation of weak zone [2]. Also, this deficiency generated because of non-uniform distribution of nano silica in pre-mix samples. The higher surface area of nano silica tends to increase the water demand thus reducing the workability which is dominant in case of pre-mix samples.

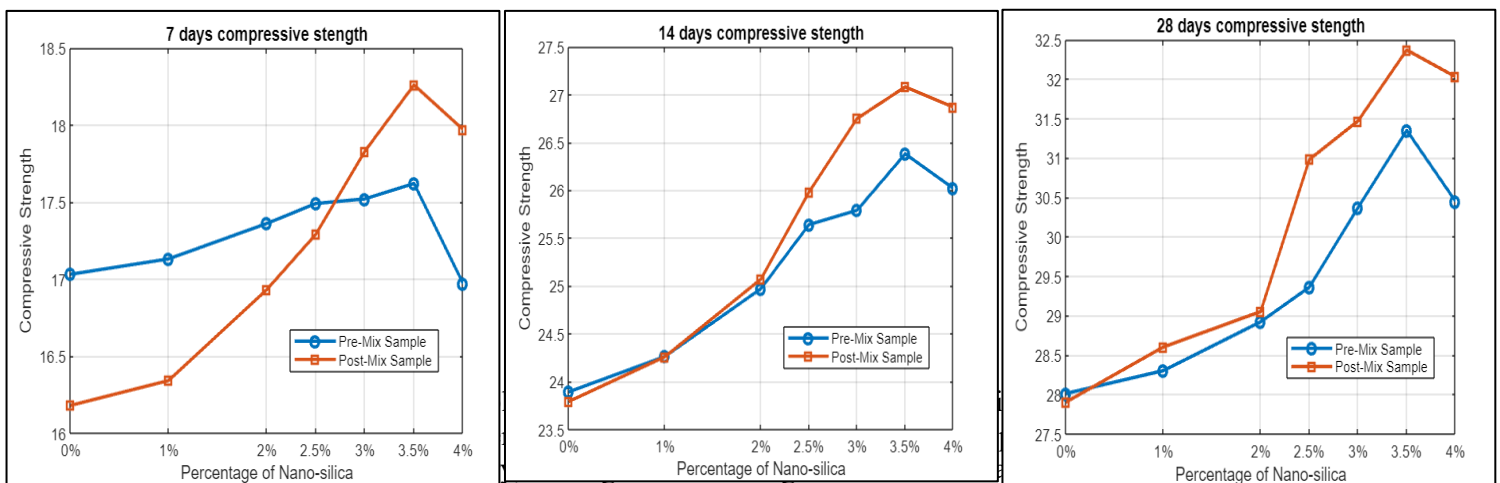


Figure 5: Compressive strength of pre-mix and post-mix samples for (a) 7 days, (b) 14 days and (c) 28 days

Cementitious matrix, comprising the mixture's strength without contributing its own. The initial increase in pre-mix samples strength at 7 days was due the increased strength obtained of cubes initial sample with greater value. Also, it was noted that the strength increment with initial percentage (mainly for sample CDS2 and CWS2 for pre-mix and post-mix respectively) was less in the initial days.

4. Conclusion

The major conclusion drawn from the study includes:

The present study aimed to investigate the influence of incorporating nano silica on the strength of pre-mix and post-mix concrete samples. The study revealed that the addition of 3.5% nano silica to both pre-mix and post-mix samples resulted in a significant increase in strength. However, it was observed that further addition of nano silica led to a decrease in strength for both types of samples.

In addition, the study highlighted that non-uniform distribution of nano silica in pre-mix samples resulted in weak zones, thereby leading to lower strength as compared to post-mix samples. Furthermore, the researchers found that the strength increment of post-mix samples was higher than that of pre-mix samples. Specifically, post-mix samples showed a strength increase of 12.85%, 13.83%, and 16.02% for 7, 14, and 28 days, respectively. In contrast, pre-mix samples had a narrow range of strength increase, ranging from 3.47% to 11.93% for the same period.

Based on the findings, it is recommended to use the post-mix method for incorporating nano materials in concrete mixtures to achieve the desired strength. The study provides meaningful insights into the effects of nano silica on the strength of concrete, which can help improve the quality of concrete structures and ensure their durability.

5. Reference

- [1]. Shaikh, F., Chavda, V., Minhaj, N., & Arel, H. S. (2018). Effect of mixing methods of nano silica on properties of recycled aggregate concrete. *Structural Concrete*, 19(2), 387–399. <https://doi.org/10.1002/suco.201700091>
- [2]. Tawfik, T. A., Abd EL-Aziz, M. A., Abd El-Aleem, S., & Serag Faried, A. (2018). Influence of nanoparticles on mechanical and non-destructive properties of high-performance concrete. *Journal of the Chinese Advanced Materials Society*, 6(4), 409–433. <https://doi.org/10.1080/22243682.2018.1489303>
- [3]. Ghafari, E., Costa, H., Júlio, E., Portugal, A., & Durães, L. (2014). The effect of nanosilica addition on flowability, strength and transport properties of ultra high performance concrete. *Materials and Design*, 59, 1–9. <https://doi.org/10.1016/j.matdes.2014.02.051>
- [4]. Lü, Q., Qiu, Q., Zheng, J., Wang, J., & Zeng, Q. (2019). Fractal dimension of concrete incorporating silica fume and its correlations to pore structure, strength and permeability. *Construction and Building Materials*, 228. <https://doi.org/10.1016/j.conbuildmat.2019.116986>
- [5]. J. Esmacili* K. Andalibi. (2012). Investigation of the effects of nano-silica on the properties of concrete in comparison with micro-silica. www.SID.ir
- [6]. Tawfik, T. A., Aly Metwally, K., EL-Beshlawy, S. A., Al Saffar, D. M., Tayeh, B. A., & Soltan Hassan, H. (2021). Exploitation of the nanowaste ceramic incorporated with nano silica to improve concrete properties. *Journal of King Saud University - Engineering Sciences*, 33(8), 581–588. <https://doi.org/10.1016/j.jksues.2020.06.007>