

Third-Body Wear Behavior of Orthopaedic Biopolymers

Binnur Sagbas, M. Numan Durakbasa

Yildiz Technical University, Department of Mechanical Engineering,
34349 Besiktas, Istanbul, Turkey
Vienna University of Technology,
Department of Interchangeable Manufacturing and Industrial Metrology,
Karlsplatz 13/3113 A-1040 Wien, Austria
bsagbas@gmail.com; aum@mail.ift.tuwien.ac.at

Abstract –Third-body wear of orthopedic materials is very important parameter that affects the service life of artificial joints. UHMWPE has been the most preferred acetabular cup material for the past four decades. However wear is the primary problem waiting for to be solved. The wear debris of UHMWPE causes adverse tissue reactions and third-body wear damages which cause implant failure. For enhancement of UHMWPE tribological properties new materials such as vitamin E blended UHMWPE (VE-UHMWPE) have been developed for extending the implants life. Although many researches have been done about tribological behavior of conventional UHMWPE, there are limited numbers of study about third-body wear mechanism of vitamin E blended UHMWPE (VE-UHMWPE). The objective of this study is to determine the effect of PMMA bone cement as third-body particles on wear behavior of conventional UHMWPE and VE-UHMWPE. Pin-on-disc wear tests were applied under 60 N load and 3 hours in ultrapure water lubrication conditions. The results were evaluated for determining wear mechanism of disc materials.

Keywords: biotribology, UHMWPE, vitamin E, third-body wear orthopaedic implant

1. Introduction

Wear is the primary problem that limits service life of orthopaedic implants. The wear debris generated during articulation of joint materials such as UHMWPE, metallic or ceramic counter face could cause adverse tissue reactions, aseptic loosening, osteolysis and at the end implant loss [Hu et al., 2001, Bergmann et al. 2001, Rocchi et al.2007, Dong et al., 2007]. So, osteolysis and related aseptic loosening are significant problem limiting the lifetime of artificial hip and knee joints [Dowd et al., 2000, Dumbleton et al., 2002]. Understanding the biotribological characteristics of the biomaterials is crucial for development of future implants [Sujet et al. 2009].

Because of its excellent biocompatibility, impact load damping properties, chemical stability and low friction coefficient UHMWPE has been the most preferred acetabular cup material for the past four decades [Bhatt, Goswami, 2008, Xiong, Ge, 2011]. However wear is the most important problem waiting for to be solved. The wear debris of UHMWPE causes adverse tissue reactions and third-body wear damages which cause implant failure. Research has been done for enhancement of UHMWPE properties such as low friction coefficient, third-body wear resistance, generation of small amounts of wear debris, and low cellular reactions to wear debris [Minakawa et al., 1998]. These enhancements are important for extending the implants life, especially for young and more active patients [Renö,Cannas, 2006]. With the modification of the UHMWPE microstructure by radiation-induced cross-linking, and various thermal treatments, first generation cross-linked UHMWPEs have been developed. [Vaidya et al.2011,Tipper et al., 2006, Bergstrom, Bischoff, 2010]. Radiation cross-linked UHMWPE has shown higher wear resistance than that of conventional UHMWPE but mechanical properties such as ultimate tensile strength, yield strength and oxidation resistance have decreased [Dong et al., 2007, Jacobs et al., 2007, Bradford et al., 2004, Furmanski et al., 2007, Sagbas, Durakbasa, 2013]. As a result of this delamination

problem commonly occurs and it accelerates wear of prosthesis [Micheli et al.,2012]. Also oxidation of UHMWPE causes decreasing of abrasive wear resistance of the material [Bracco, Oral, 2011, Blunn et al., 2002]. For eliminating these negations second generation cross-linked UHMWPEs have been introduced which have been obtained by adding α -tocopherol or vitamin E, as a natural antioxidant, into UHMWPE to reduce the problems caused by the post irradiation thermal treatment [Vaidya et al.2011]. In previous studies it was reported that the addition of vitamin E increases oxidation and delamination resistance of UHMWPE while maintaining the mechanical properties by stabilizing the residual free radical with eliminating post-irradiation melting process [Bracco, Oral, 2011, Oral et al., 2006a, Oral et al., 2004, Oral et al., 2006b].

Literature works about retrieved prosthesis show that third-body wear is a very important parameter affecting the service life of artificial joints [Bragdon et al, 2003]. By scratching the metal femoral head and femoral component of total hip and knee prosthesis third body particles promote the wear rate of UHMWPE acetabular cup and tibial component. PMMA bone cement particles are believed to be the main cause of third-body particles [Wang, Essner, 2001]. Besides, bone particles, metal beads or fibers from porous coatings and hydroxyapatite coatings, corrosion products from the metal tapers and metal fragments from other fixation devices may be the source of third body particles. [Hirakawa et al., 2004, Kim et al, 2005, Mackay et al, 2000, Willie et al., 2000, Que, Topoleski, 2000] Although many researches have been done about tribological behavior of conventional UHMWPE, there are limited numbers of study about third-body wear mechanism of vitamin E blended UHMWPE (VE-UHMWPE). The objective of this study is to determine the effect of PMMA bone cement as third-body particles on wear behavior of conventional UHMWPE and VE-UHMWPE in ultrapure water lubrication conditions and comparing the results in terms of disc materials.

2. Materials and Methods

UHMWPE and VE-UHMWPE disc samples were machined from Chirulen 1020 and Chirulen 1020 E rods (MediTECH Medical Polymers, Vreden, Germany) in 40 mm diameter and 5 mm thickness in accordance with ASTM G99-05. CoCrMo pin samples were used as counter face. Mechanical properties of UHMWPE, VE-UHMWPE and CoCrMo materials can be seen in table 1. Surface roughness of the samples was measured by Taylor Hobson Form Talysurf Intra. Average surface roughness of UHMWPE samples was 0.678 μm , of VE-UHMWPE was 0.653 μm . Pin-on-disc tribotester was used for wear tests and friction coefficient measurements. 60 N static load was applied with the frequency of motion 1 Hz and the tests were run up to 3 h. The tests were conducted in ultrapure water lubrication conditions.

Table. 1. Mechanical properties of UHMWPE, VE-UHMWPE and CoCrMo

Variable	Unit	UHMWPE	VE-UHMWPE	CoCrMo
		Average	Average	Average
Density	Kg/m ³	936	937	8270
Young's Modulus	MPa	660	683	200
Poisson's Ratio	-	0.46	0.46	0.3

The disk samples were cleaned in an ultrasonic bath, at 30° C, 15 min. in ultrapure water than 30 min. in ethyl alcohol at the end 15 min. ultrapure water respectively.

CoCrMo pin samples were manufactured in 5 mm diameter and 12 mm length. The tips of the pins were rounded in 5 mm diameter for obtaining higher contact pressure and homogeneous distribution of this pressure. Tip surface of the pins were polished by using 800,1000,1200 and 2000 grid sand papers. The average surface roughness of the samples were about 0,5 μm . The pins were cleaned in an ultrasonic bath, 15 min. in ultrapure water than 30 min. in acetone at the end 15 min. ultrapure water respectively. Drawing of manufactured pin samples can be seen in fig. 1.

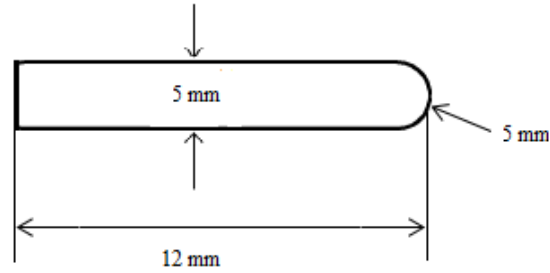


Fig. 1. Drawing of CoCrMo pin samples

The diameters of the PMMA bone cement particles were measured by a particle size analyzer Malvern Nano ZS10 Zeta Sizer Nano Series (Malvern Instruments). The diameter of the PMMA particles changes between 264.3 nm and 412.5 nm and the average size of the diameters was about 339 nm. The morphological image of the PMMA particles, taken by Leica DCM 3D microscope, can be seen in Fig. 2. As can be seen in this figure, the particles have smooth spherical shape. These particles were mixed with ultrapure water by using magnetic stirrer for preparing the wear test lubricant and the concentration of the solution was 10 g/l. Ultrapure water without PMMA particles was used for control.

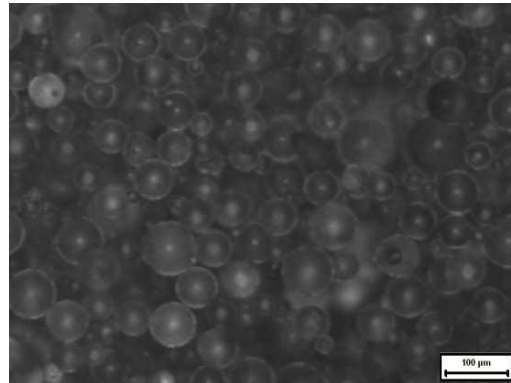


Fig. 2. Microscope image of the PMMA particles used as third-body abrasive particle in wear tests

Wear track profile area was measured by Dektak 6 M Stylus Profiler for determining wear amount of the disc surfaces (fig. 3 and fig.4). After wear tests the worn surfaces were analyzed by Keyence VHX Digital Microscope.

By using cross-sectional area of wear track and its radius the wear volume was calculated. Then by using Eq. (1) wear factor (k) of each disc sample was determined.

$$k = \frac{V}{N.S} \quad (1)$$

k; wear factor ($\text{mm}^3/\text{N.m}$), V; wear volume (mm^3), N; applied load (N), S; friction distance (m) [Ma et al., 2009, Pylios, Shepherd, 2008].

3. Results and Discussion

Friction coefficient of the pin-on-disc wear tests can be seen in fig.5. Wear factor k for UHMWPE was $3,28 \times 10^{-5} \text{ mm}^3/\text{N.m}$, for UHMWPE samples with PMMA third-body particles k became $4,90 \times 10^{-5} \text{ mm}^3/\text{N.m}$. For VE-UHMWPE disc samples without PMMA particles the wear factor was $3,00 \times 10^{-5} \text{ mm}^3/\text{N.m}$ and for VE-UHMWPE with PMMA particles k was $3,35 \times 10^{-5} \text{ mm}^3/\text{N.m}$. Friction coefficient and wear factor of UHMWPE disc samples were higher than VE-UHMWPE samples' value in just

ultrapure water lubrication condition without third-body abrasive particles. Likely, while PMMA abrasive particles were added in lubricant, friction coefficient and wear factor of two material groups were increased.

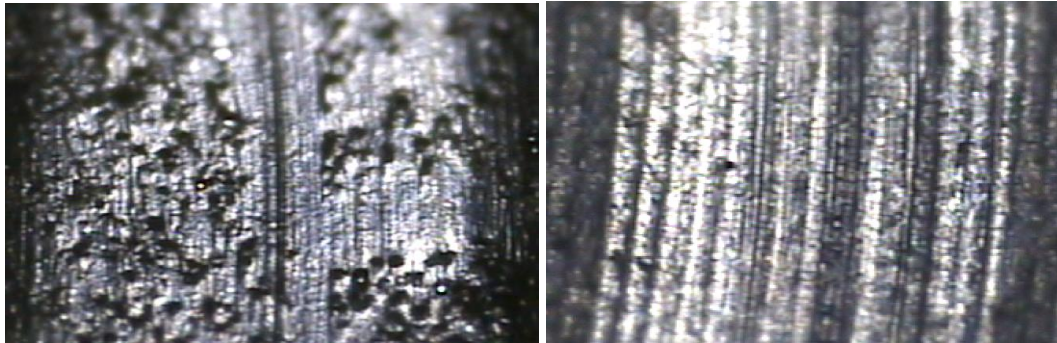


Fig. 3. Image of the wear track of UHMWPE with (a) and with out (b) PMMA third-body abrasive particles

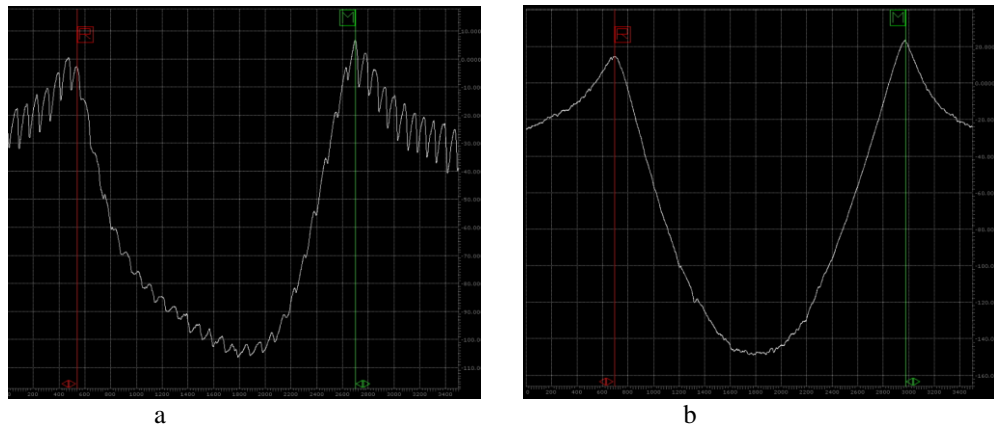


Fig. 4. Wear track profile of UHMWPE with (a) and with out (b) PMMA third-body abrasive particles

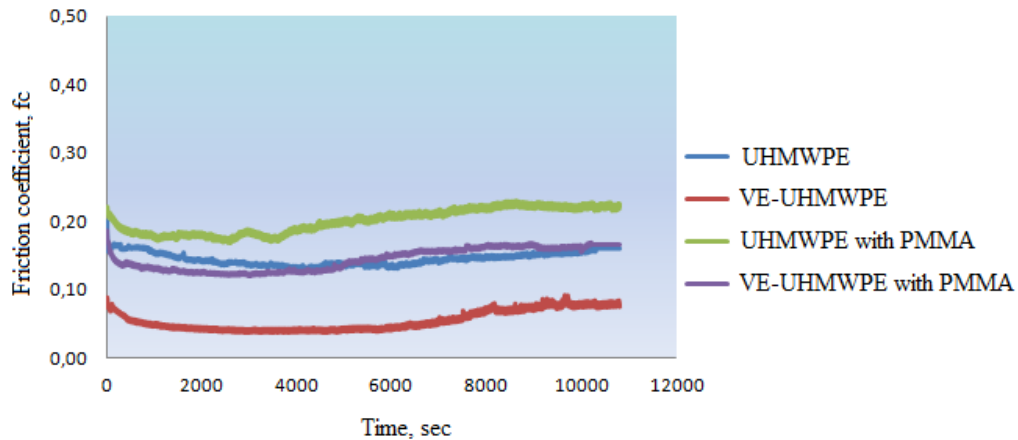


Fig. 5. Friction coefficient of disc samples with and without PMMA abrasive particles

Three possible interacting mechanisms of PMMA particles with acetabular cup and femoral head sliding surfaces after being trapped at the interface were explained in a previous study [Wang, Essner, 2001]. First, particles may embed in polyethylene surface which cause to reduce the contact between the head and the cup. In second mechanism PMMA particles may adhere to the femoral head under pressure

and lastly some particles may roll freely between the surfaces. In pin-on-disc configuration the embedded particles may cause pitting, the free particles that roll between surfaces may cause scratches on the UHMWPE disc surface as can be seen in fig. 6.

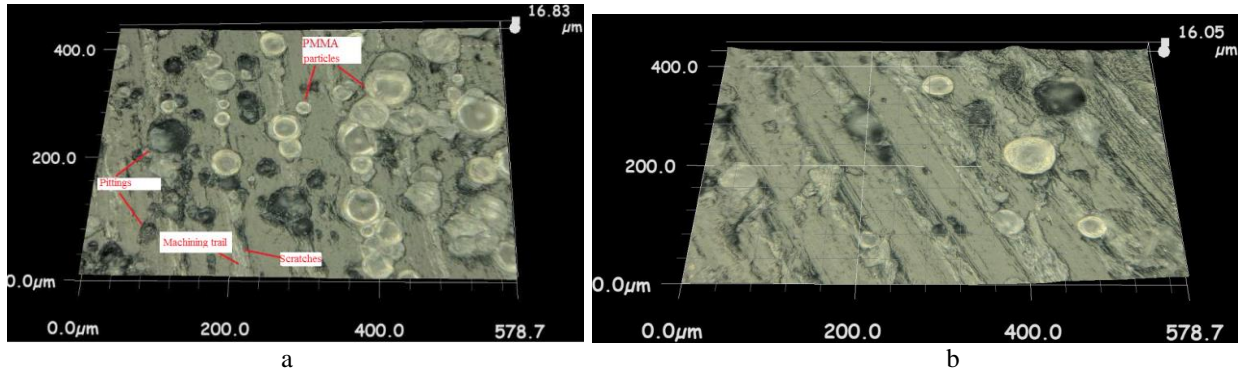


Fig. 6. 3D image of UHMWPE (a) and VE-UHMWPE (b) disc sample with PMMA particles [Sagbas, 2013].

Friction coefficient and wear factor of the VE-UHMWPE samples were lower than conventional UHMWPE. [Sakoda et al., 2006] studied with knee simulator for determining wear behavior of conventional UHMWPE and VE- UHMWPE knee prosthesis. They reported that wear of VE-UHMWPE was 30% lower than of conventional UHMWPE. Vitamin E increased the oxidation resistance UHMWPE and decreased lamination and formation of surface cracks. So friction coefficient and wear factor of VE blended UHMWPE decreased. Similarly the third-body wear amounts of VE-UHMWPE samples were lower than conventional UHMWPE. As can be seen in fig.6 amount of embedded PMMA third-body particles on conventional UHMWPE disc surface were more than on surface of VE-UHMWPE. It can be thought that vitamin E may increase the surface properties of UHMWPE.

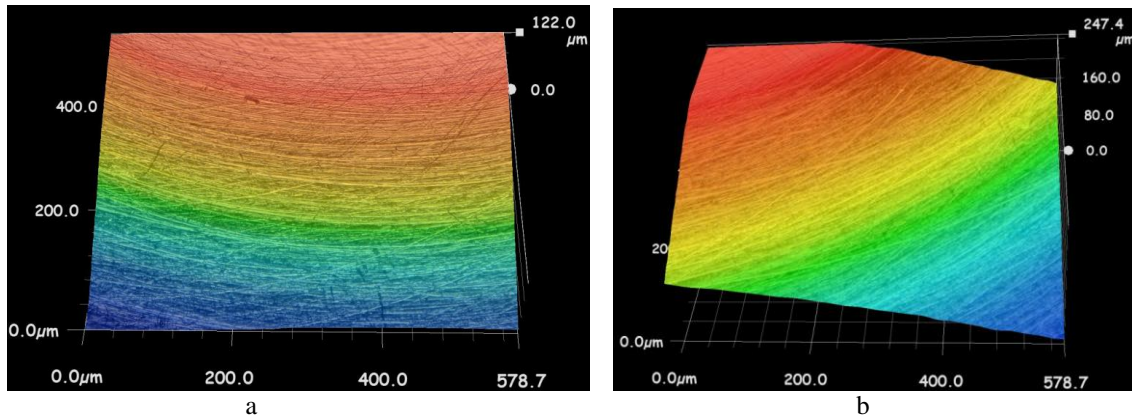


Fig. 7. Microscopic images of pin surface after wear tests with PMMA (a) and without PMMA particles (b).

Microscopic images of pin surface after wear tests can be seen in fig.7. Scratches were visible on pin surface which tested in PMMA third-body lubrication condition. There were fewer scratches on without PMMA testing condition pin surface.

4. Conclusion

Although new materials have been developed for enhancement of UHMWPE tribological properties, wear is the primary factor that affecting the service life of implant. The wear debris of UHMWPE causes adverse tissue reactions and third-body wear damages which cause implant failure. For determining third-body wear mechanism of second generation UHMWPE, pin-on-disc wear tests were done. The results show that wear factor and friction coefficient of VE-UHMWPE was smaller than conventional

UHMWPE. PMMA particles used as third-body abrasive material increased the wear rate of both material groups. Surface properties of VE-UHMWPE were better than conventional UHMWPE. The amount of embedded PMMA third-body particles on conventional UHMWPE disc surface were more than on surface of VE-UHMWPE. It can be thought that vitamin E may increase the surface properties of UHMWPE.

Acknowledgments

This research has been supported by Yildiz Technical University Scientific Research Projects Coordination Department. Project number: 2011-06-01-DOP03. The authors would like to thank Interchangeable Manufacturing and Industrial Metrology and Nanometrology Laboratory at the Vienna University of Technology, Wien, Austria, for support of surface measurements.

6. References

- ASTM G99-05 (2010). Standard Test Method for Wear Testing with a Pin-on-Disk Apparatus.
- Bergmann, G., Graichen, F., Rohlmann, A., Verdonschot, N., & van der Lende, G.H. (2001). Frictional Heating Of Total Hip Implants Part 2: Finite Element Study. *Journal of Biomechanics*, 34, 429–435.
- Bergstrom, J.S., & Bischoff, J. E. (2010). An Advanced Thermo Mechanical Constitutive Model For UHMWPE. *International Journal of Structural Changes in Solids– Mechanics and Applications*, 2(1), 31,39.
- Bhatt, H., & Goswami, T. (2008). Implantwearmechanisms—Basic Approach. *Biomedical Materials*, 31–9.
- Blunn, G., Brach del Preva, E. M., Costa, L., Fisher, J., & Freeman, M. A. R. (2002). Ultra High Molecular-Weight Polyethylene (UHMWPE) In Total Knee Replacement: Fabrication, Sterilisation And Wear. *Journal of Bone Joint Surgery British*, 84, 946-949.
- Bracco, P., & Oral, E. (2011). Vitamin E-stabilized UHMWPE for Total Joint Implants. *Clinical Orthopaedics and Related Research*, 469, 2286–2293.
- Bradford, L., Baker, D.A., Graham, J., Chawan, A., Ries, M.D., & Pruitt, L.A. (2004). Wear and Surface Cracking in Early Retrieved Highly Cross-Linked Polyethylene Acetabular Liners. *The Journal of Bone & Joint Surgery*, 86(6), 1271-1282.
- Bragdon, C., Jasty, M., Muratoglu, O., O'Connor, D., & Harris, W. (2003). Third-Body Wear Of Highly Cross-Linked Polyethylene In A Hip Simulator. *J. Arthroplasty*, 18, 553–561.
- Dong, G.N., Hua, M., Li, J., & Chuah, K.B. (2007). Temperature Field And Wear Prediction For UHMWPE Acetabular Cup With Assumed Rectangular Surface Texture. *Materials and Design*, 28, 2402–2416.
- Dowd, J.E., Sychterz, C.J., Young, A.M., & Engh, C.A. (2000). Characterization Of Long-Term Femoral-Head-Penetration Rates. Association With And Prediction Of Osteolysis. *Journal of Bone Joint Surgery—American Volume*, 82(A), 1102–1107.
- Dumbleton, J.H., Manley, M.T., & Edidin, A.A. (2002). A Literature Review Of The Association Between Wear Rate And Osteolysis In Total Hip Arthroplasty. *Journal of Arthroplasty*, 17, 649–61.
- Furmanski, J., Gupta, S., Chawan, A., Kohm, A., Lannutti, J., Jewett, B., Pruitt, L.A., & Ries, M.D. (2001). Aspherical Femoral Head With Highly Cross-Linked Ultra-High Molecular Weight Polyethylene Surface Cracking. *The Journal of Bone & Joint Surgery*, 89, 2266-2270.
- Hirakawa, K., Jacobs, J.J., Urban, R., & Saito, T. (2004). Mechanisms Of Failure Of Total Hip Replacements: Lessons Learned From Retrieval Studies. *Clinical Orthopaedics and Related Research*, 420, 10–17.
- Hu, C.C., Liao, J.J., Lung, C.Y., Huang, C.H., & Cheng, C.K. (2001). A Two Dimensional Finite Element Model For Frictional Heating Analysis Of Total Hip Prosthesis. *Materials Science and Engineering C*, 17, 11–18.
- Jacobs, C.A., Christensen, C.P., Greenwald, A.S., & McKellop, H. (2007). Clinical Performance of Highly Cross-Linked Polyethylenes in Total Hip Arthroplasty. *The Journal of Bone & Joint Surgery Am*, 89, 2779-2786.

- Joshi, A., Ilchmann, T., & Markovic, L. (2001). Socket Wear In Bilateral Simultaneous Total Hip Arthroplasty. *Journal of Arthroplasty*, 16, 117–120.
- Kim, Y.H., Ritchie, A., & Hardaker, C. (2005). Surface Roughness Of Ceramic Femoral Heads After In Vivo Transfer Of Metal: Correlation To Polyethylene Wear. *Journal of Bone and Joint Surgery*, 87, 577–582.
- Ma, L., Rainforth, V.M., Sun, D., Wharton, J.A., & Wood, R.J.K. (2009). A ‘3-Body’ Abrasion Wear Study Of Bioceramics For Total Hip Joint Replacements. *Wear*, 267, 2122–2131.
- Mackay, D., Gower, A., Mawhinney, B., Gregg, P.J., & McCaskie, A.W. (2000). Metallic Instrument Debris: A Source Of Third-Body Wear Particles? *Journal of Arthroplasty*, 15, 816–818.
- Micheli, B. R., Wannomae, K. K., Lozynsky, A. J., Christensen, S. D., & Muratoglu, O. K. (2012). Knee Simulator Wear Of Vitamin E Stabilized Irradiated Ultrahigh Molecular Weight Polyethylene. *The Journal of Arthroplasty*, 27, 95-104.
- Minakawa, H., Stone, M.H., Wroblewski, B.M., Lancaster, J.G., Ingham, E., & Fisher, J. (1998). Quantification Of Third Body Damage And Its Effect On Uhmwpe Wear With Different Types Of Femoral Head. *Journal of Bone and Joint Surgery British*, 80(5), 894–902.
- Oral, E., Christensen, S.D., Malhi, A.S., Wannomae, K.K., & Muratoglu, O.K. (2006). Wear Resistance and Mechanical Properties of Highly Cross-linked, Ultrahigh–Molecular Weight Polyethylene Doped With Vitamin E. *Joint Arthroplasty*, 4, 580-591.
- Oral, E., Rowell, S.L., & Muratoğlu, O.K. (2006). The Effect Of A-Tocopherol On The Oxidation And Free Radical Decay In Irradiated Uhmwpe. *Biomaterials*, 27(32), 5580–5587.
- Oral, E., Wannomae, K.K., Hawkins, N., Harris, W.H., & Muratoglu, O.K. (2004). Alpha- Ocoferol-Doped Irradiated UHMWPE For High Fatigue Resistance And Low Wear. *Biomaterials*, 25(24), 5515-22.
- Pylios, T., & Shepherd, D. E. T. (2008). Wear Of Medical Grade Silicone Rubber Against Titanium And Ultrahigh Molecular Weight Polyethylene. *Inc. J Biomed Mater Res Part B: Appl. Biomater*, 84B, 520–523.
- Que, L., & Topoleski, L.D. (2000). Third-Body Wear Of Cobalt–Chromium– Molybdenum Implant Alloys Initiated By Bone And Poly(Methyl Methacrylate) Particles. *Journal of Biomedical Materials Research*, 50, 322–330.
- Renò, F., & Cannas, M., (2006). UHMWPE And Vitamin E Bioactivity: An Emerging Perspective. *Biomaterials*, 27(16), 3039–3043.
- Rocchi, M., Affatato, S., Falasca, G., & ve Viceconti, M. (2007). Thermomechanical Analysis Of Ultra-High Molecularweight Polyethylene-Metal Hip Prostheses. *Proceedings of the Institution of Mechanical Engineers Part H Journal of Engineering in Medicine*, 221, 561-568.
- Sagbas, B. (2013). Measurement, Analysis And Metrological Evaluation Of Physical Magnitudes And Geometrical Features That Show Alteration With Regard To Friction In Hip Prosthesis. *Ph.D. Thesis*, Yildiz Technical University, Istanbul, Turkey.
- Sagbas, B., & Durakbaşa, M.N. (2013). Effect of Surface Patterning on Frictional Heating of Vitamin E Blended UHMWPE. *Wear*, 303, 313–320.
- Sakoda, H., Nono, D., Kuramoto, K., Suzuki, M., Moriya, H., & Tomita, N. (2006). Superior Wear Resistance Of Vitamin E Added Uhmwpe Tested On Knee Joint Simulator. *52nd Annual Meeting of the Orthopaedic Research Society*, 19-22.
- Sujeet, K., Sinha, B., & Briscoe, J. (2009). *Polymer Tribology*, Imperial College Press, ISBN -13 978-1-84816-202-0, pp.259.
- Tipper, J. L., Galvin, A. L., Williams, S., McEwen, H. M. J., Stone, M. H., Ingham, E., & ve Fisher, J., (2006). Isolation And Characterization Of UHMWPE Wear Particles Down To Ten Nanometers In Size From In Vitro Hip And Knee Joint Simulators. *J. Biomed. Mater. Res., Part A*, 78A(3), 473–480.

- Vaidya, C., Alvarez, E., Vinciguerra, J., Bruce, D.A., & DesJardins, J.D. (2011). Reduction Of Total Knee Replacement Wear With Vitamin E Blended Highly Cross-Linked Ultra- High Molecular Weight Polyethylene. *Proceedings of the Institution of Mechanical Engineers Part H: Journal of Engineering in Medicine*, 225, 1–7.
- Wang, A., & Essner, A. (2001). Three-Body Wear Of UHMWPE Acetabular Cups By PMMA Particles Against CoCr, Alumina And Zirconia Heads In A Hip Joint Simulator. *Wear*, 250, 212–216.
- Willie, B.M., Shea, J.E., Bloebaum, R.D., & Hofmann, A.A. (2000). Elemental And Morphological Identification Of Third-Body Particulate And Calcium Stearate Inclusions In Polyethylene Components. *Journal of Biomedical Materials Research*, 53, 137–142.
- Xiong, D., & Ge, S. (2011). Friction And Wear Properties Of UHMWPE/Al₂O₃ Ceramic Under Different Lubricating Conditions. *Wear*, 250, 242–245.